

Field Re-entrant Superconductivity Induced by the Enhancement of Effective Mass in URhGe

Atsushi MIYAKE^{1,2*}, Dai AOKI¹, and Jacques FLOUQUET¹

¹INAC/SPSMS, CEA-Grenoble, 17 rue des Martyrs, 38054 Grenoble, France

²KYOKUGEN, Osaka University, Toyonaka, Osaka 560-8531, Japan

(Received August 18, 2008)

High quality single crystals of a ferromagnetic superconductor URhGe were successfully grown. The electrical resistivity was measured for the field along b -axis in the orthorhombic crystal structure in order to study precisely its field re-entrant superconductivity which occurs in the vicinity of the field H_R , where the easy magnetization switches from c to b -axis. The field re-entrant superconductivity of URhGe is analyzed with special focus on its dependence with the value of residual resistivity ρ_0 and the coefficient A of T^2 term of the resistivity. The experimental results are well explained by a crude model related with the field dependence of the effective mass m^* , where the corresponding critical temperature $T_{sc}(m^*)$ and the upper critical field H_{c2} are strongly enhanced. Discussion is made on the interplay between magnetic and superconducting phase diagram as well as the link between T_{sc} and A in other heavy fermion superconductors.

KEYWORDS: Field re-entrant superconductivity, URhGe, Ferromagnetic superconductor, Effective mass

1. Introduction

Ferromagnetism and superconductivity had been thought to be mutually competitive phenomena, since the large internal field easily destroys the Cooper pair for conventional superconductivity. In 1970s, the superconductivity was found in $4f$ -localized ferromagnets, such as ErRh_4B_4 ,^{1,2} where the superconducting critical temperature T_{sc} is larger than the Curie temperature T_{Curie} . Below T_{Curie} , the superconducting phase is expelled, thus the both phases are competing with each other. In these systems with two separated electronic bath (localized $4f$ electrons and light itinerant electrons), the ferromagnetism is a robust quantity even for $T_{\text{Curie}} < T_{sc}$. The discovery of superconductivity in the $5f$ -itinerant ferromagnet UGe_2 under pressures was one of the breakthrough in the unconventional superconductivity.³ Contrary to ErRh_4B_4 , T_{sc} is lower than T_{Curie} in UGe_2 and the superconductivity exists only in the ferromagnetic phase on the pressure-temperature phase diagram, where the superconductivity coexists with the ferromagnetism. The triplet superconductivity with equal spin pairing is, therefore, believed, because the large internal field will not prevent the formation of the Cooper pair.

Other examples for the coexistence of ferromagnetism and superconductivity are URhGe ⁴ and the recently found UCoGe ,^{5,6} which crystallize in the orthorhombic structure with TiNiSi -type. In the case of URhGe , the ferromagnetic (FM) transition occurs at $T_{\text{Curie}} = 9.5\text{ K}$ and its ordered moment is $M_0 = 0.4\mu_B/\text{U}$. The superconductivity (SC) was found to exist below $T_{sc} = 0.25\text{ K}$ at ambient pressure.⁴ The upper critical fields H_{c2} are larger than the Pauli limiting field, thus the spin-triplet state is most likely realized.⁷ Striking feature is the field re-entrant superconductivity (RSC).^{8,9} With increasing the magnetic field along the b -axis in the orthorhom-

bic structure, the moment starts to tilt from the easy magnetization c -axis to b -axis, and then the ordered ferromagnetic moment is completely aligned to the b -axis above a reorientation field $H_R = 12\text{ T}$. The RSC is observed between $H_1 = 8$ and $H_2 = 12.7\text{ T}$ and detected in wide range of the field angle around $H \parallel b$. Thus, this superconductivity is not due to the so-called Jaccarino-Peter effect,¹⁰ which has been found in the Chevrel phase compound¹¹ and the organic superconductors, such as $\kappa\text{-(BETS)}_2\text{FeBr}_4$,¹² where the RSC is due to a compensation of the external field by the internal exchange field.

An enhancement of H_{c2} related to the metamagnetic transition has been observed in the ferromagnetic superconductor UGe_2 , as well.¹³ When the magnetic field is applied along the easy-magnetization axis (a -axis) at a pressure of $P = 1.35\text{ GPa}$, the ferromagnetic phase changes from FM1 (weakly polarized phase) to FM2 (strongly polarized phase) at H_x with increasing field. The H_{c2} - T phase diagram shows the step-like increase of H_{c2} at H_x and $H_{c2}(0)$ in FM2 is higher than that expected in FM1.

Here we report the careful studies on the field dependence of the inelastic T^2 term A of the electrical resistivity ρ by using the high quality single crystals in order to study the RSC of URhGe . The resistivity follows the quadratic temperature dependence, namely $\rho = \rho_0 + AT^2$ for all the measured field range. The RSC is well explained by the enhancement of the effective mass m^* .

2. Experimental

The single crystals of URhGe were grown by the Czochralski pulling method in the radio frequency furnace under purified Ar atmosphere gas with a stoichiometric ratio of the starting materials, U (Purity: 3N-99.9%), Rh (4N) and Ge (6N). The ingot was annealed at 1300°C under ultra high vacuum (UHV) for one day. The single crystal ingot was oriented by the Laue photo-

*E-mail address: atsushi.miyake@cea.fr

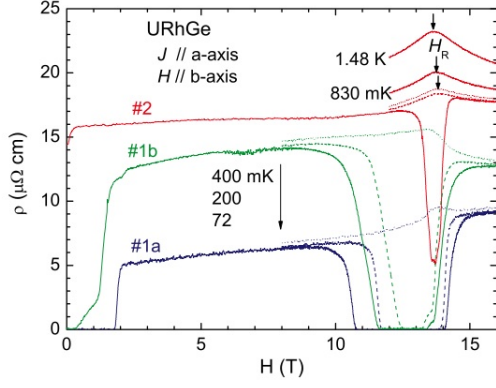


Fig. 1. (Color online) Field dependences of the resistivity at constant temperatures in sample #1a, #1b and #2 for the current along a -axis and the field along b -axis. The solid, dashed and dotted lines show the data at 72, 200 and 400 mK, respectively. For sample #2, the data at 830 mK and 1.48 K are displayed as well. The arrows indicate the reorientation field H_R .

graph and was cut by the spark cutter. The samples were annealed again at 900 °C in the electrical furnace under UHV for 20 days. The electrical resistivity was measured by the four probe AC method at low temperatures down to 70 mK and at high magnetic fields up to 16 T. The electrical current and magnetic fields were applied along a - and b -axis, respectively. We carried out the resistivity measurements by using two single crystals. The sample (#1) with two pairs of voltage contacts (#1a and #1b) and the other sample with one pair of voltage contact (#2) are employed. This allows us to compare two sets of data (#1a and #1b) with different residual resistivity in the same crystal without misalignment between sample #1a and sample #1b. The residual resistivity ratios ($RRR = \rho_{RT}/\rho_0$) are 40, 16 and 12, respectively, for sample #1a, #1b and #2, indicating the high quality single crystals.

3. Results and Discussion

Figure 1 represents the field dependence of the resistivity ρ for #1a, #1b and #2 at 72, 200 and 400 mK. For sample #1a with $RRR = 40$, the RSC was clearly observed between $H_1 = 10.7$ T and $H_2 = 14.2$ T at 72 mK, where H_1 and H_2 are defined as mid points of the drop of resistivity. At high temperature of 400 mK, the resistivity shows the peak at $H_R = 13.7$ T, corresponding to the reorientation of the moment. The crystal seems to misalign slightly from the field direction respect to the b -axis, because H_1 , H_2 and H_R are larger than those in the previous reports.^{8,9} The purer sample, i.e. higher value of RRR , shows the wider superconducting windows and the higher transition temperatures. It is interesting to note that for sample #2, only track of SC is suspected at low field, while rather deeper drop on the resistivity is observed in a very narrow field window. The same trend is observed in sample #1b, where the resistivity shows rather sharp drop due to the RSC, although the step-like behavior is observed near H_{c2} for the low field SC. These

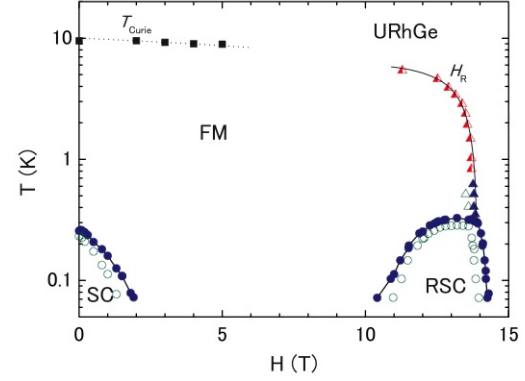


Fig. 2. (Color online) Temperature-field phase diagram of the low field superconductivity (SC), the re-entrant SC (RSC) and reorientation field H_R for $H \parallel b$ in URhGe. The circles display the critical field (temperature) of the superconductivities defined as a midpoint of the resistivity drop. The triangles correspond to the reorientation field H_R defined as a peak of the $\rho(H)$ curves. The solid squares are ferromagnetic transition temperature T_{Curie} cited from Ref. 16. The dark blue (filled symbol), green (open) and red (half filled) correspond to the results for sample #1a, #1b and #2, respectively. The lines are guides for eyes.

observation indicates the strict condition for RSC. That suggests a strong increase of the coherence length in the RSC phase. On the other hand, the reorientation field H_R are not sensitive to the sample quality. The insensitivity is also a FM property at zero field.⁴ It is noted that H_1 is more sensitive to the sample quality compared to H_2 , indicating that the RSC strongly stick to H_R .

Figure 2 shows the superconducting phase diagram and reorientation field H_R . In sample #1a, the upper critical field $H_{c2}(0) = 2$ T is clearly larger than the Pauli limiting field $H_p = 0.46$ T estimated from $T_{sc}(0) = 0.25$ K, indicating that H_{c2} is determined by the orbital limit depending on the effective mass. The RSC is observed between $H_1 = 10.7$ and $H_2 = 14.2$ T at 72 mK for sample #1a. It is interesting that $T_{sc}(H)$ for RSC reaches a temperature of 330 mK at 13.3 T, which is larger than the value of $T_{sc}(0) = 250$ mK at zero field. This peculiar behavior is consistent with the analysis of T_{sc} by the enhancement of effective mass m^* in Fig. 6 as discussed later. At high temperatures, the reorientation field H_R starts to decrease with increasing temperature. Finally, H_R seems to be connected to the Curie temperature $T_{Curie} = 9.5$ K at zero field.

Figure 3 represents the variations of H_{c2} , H_1 , H_2 and H_R at 72 mK as a function of ρ_0 , which is inversely proportional to the mean free path, i.e. $\rho_0 \propto 1/l$. For unconventional superconductivity like URhGe, the T_{sc} must depend on the variation of the parameter ξ/l between the superconducting coherence length ξ and l according to the Abrikosov-Gor'kov pair breaking mechanism,¹⁴ where l must be larger than the coherence length ξ . The so-called clean limit condition must be satisfied. Such a dependence has been actually observed in previous studies on polycrystalline samples¹⁵ and single crys-

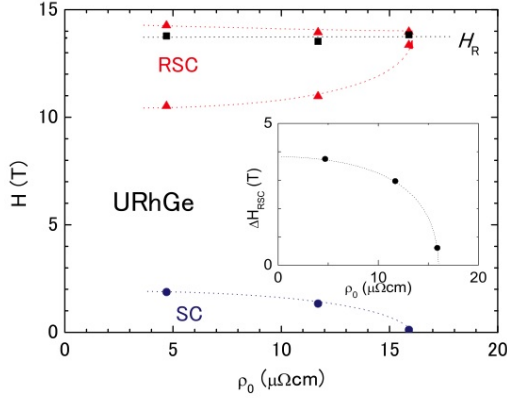


Fig. 3. (Color online) Critical fields of superconductivities, H_{c2} , H_1 and H_2 , and the reorientation field H_R as a function of the residual resistivity $\rho_0(H = 0)$ at 72mK in URhGe. The residual resistivity is inversely proportional to the mean free path l . The dark blue circle and red triangle are the critical fields of low field and re-entrant superconductivities, respectively. The black square is reorientation field H_R . The inset shows the field width of RSC, ΔH_{RSC} . The dotted lines are guides for eyes.

tals.⁷ The striking point is that the RSC also collapses when the low field SC collapses, moreover, the RSC width ΔH_{RSC} strongly depends on ρ_0 . The suppression of RSC with lower quality samples indicates that RSC as well as low field SC are unconventional.

Here we simply estimate T_{sc} for RSC from strength of the parameter ξ/l . Since the coherence length ξ is given by the relation, $\xi \sim \hbar v_F / k_B T_{sc}$, where v_F is Fermi velocity, ξ is inversely proportional to $m^* T_{sc}$. If the ξ/l is assumed to be invariant against the magnetic field, $\xi/l \propto 1/(m^* l T_{sc}) \propto \rho_0 / (m^* T_{sc}) \propto \rho_0 / (\sqrt{A} T_{sc})$ must be a constant, we can estimate the extrapolated value at zero field of the critical temperature $T_{sc}^0(m_{H_R}^*)$ for fictitious quasiparticles of mass $m_{H_R}^*$ at $H = 0$. Here we assume the Kadowaki-Woods relation between m^* and A , namely $m^* \sim \sqrt{A}$. From Fig. 4, one can obtain the ratio $(\rho_0 / \sqrt{A})_{H=H_R} / (\rho_0 / \sqrt{A})_{H=0} \sim 1.4$ and then $T_{sc}^0(m_{H_R}^*) \sim 1.4 T_{sc}^0(m_{H=0}^*)$: $T_{sc}^0(m_{H_R}^*)$ can be estimated as 350 mK from $T_{sc}^0(m_{H=0}^*) = 250$ mK. Consistent with this zero field extrapolation, the experimental result in Fig. 2 indicates $T_{sc}(m_{H_R}^*, H_R) \simeq 320$ mK for sample #1a, which is smaller than the evaluated $T_{sc}(m_{H_R}^*, H = 0)$.

As shown in Fig. 4(b), the A coefficient starts to decrease slightly and increase again with increasing field. It has a maximum just below H_R , where ρ_0 has a maximum (Fig. 4(a)), then strongly decreases. The effective mass may play an important role for the appearance of superconductivity. Thus we need to evaluate what will be the SC temperature $T_{sc}^0(m_H^*)$, assuming that the effective mass is no more the effective mass at zero field, $m_{H=0}^*$, but the mass m_H^* built by the H dressing of the quasiparticle.

It is well known that the calculation of $T_{sc}(m^*)$ is a difficult task which requires the solution of the Eliashberg equation. However, we will show that the RSC in

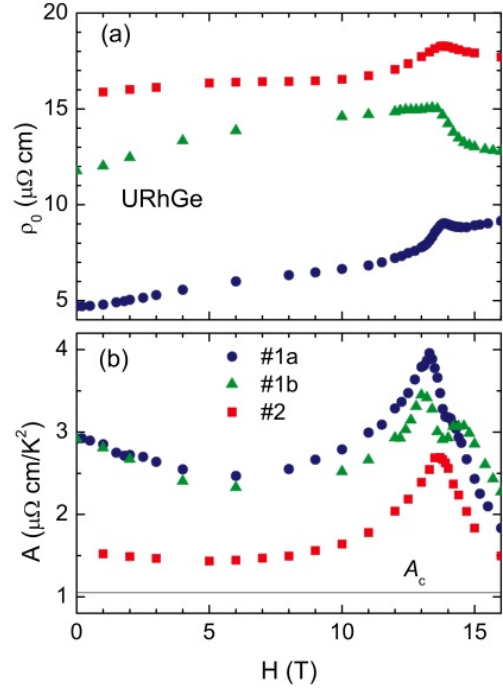


Fig. 4. (Color online) Field dependence of (a) the residual resistivity ρ_0 and (b) the coefficient A on URhGe for sample # 1a, # 1b and # 2. The values are obtained by the least square fit with $\rho(T) = \rho_0 + AT^2$ between T_{sc} and 750 mK. The horizontal line denoted by A_c in panel (b) corresponds to the square of the band mass, $(m_B)^2$, using the calculation of $T_{sc}^0(m_H^*)$ and the detail is in the text.

URhGe seems to be well explained by a crude model where T_{sc} is related to the field variation of the effective mass m_H^* . The simplicity of URhGe comes from its non-proximity to the ferromagnetic instability; the pressure (P) increases T_{Curie} , and decreases T_{sc} as well as the A coefficient.^{17,18} P and H scans show that URhGe corresponds to the simple case where the variation of the A coefficient (basically m^*) and T_{sc} are coupled, that is, the enhancement of A leads to an enhancement of T_{sc} . The chosen expression of $T_{sc}^0(m_H^*)$ is

$$T_{sc}^0(m_H^*) = T_0 \exp\left(-\frac{m_H^*}{gm^{**}}\right), \quad (1)$$

where the effective mass m_H^* is described by the band mass m_B plus an extra mass m^{**} directly related to the source of SC pairing, namely,

$$m_H^* = m_B + m^{**}. \quad (2)$$

Assuming $g = 1$ for simplicity,

$$T_{sc}(m_H^*) = T_0 \exp\left[-\left(\frac{m_B}{m^{**}} + 1\right)\right] \quad (3)$$

The expression is based on the McMillan-like formula,¹⁹ for FM superconductors, it was theoretically proposed far from FM instability.^{20–22} Taking the logarithmic derivative of eq. (3), it is interesting to remark that Grüneisen

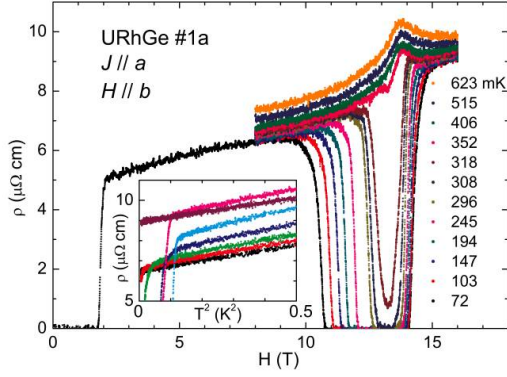


Fig. 5. (Color online) Field dependence of the resistivity on sample #1a at various temperatures. The numbers of legend indicate temperatures in the unit of mK. The inset shows T^2 -dependence of the resistivity under magnetic fields of $H = 9, 10, 11, 12, 13, 15$ and 14 T from bottom to top.

parameter for T_{sc} will be linked to the Grüneisen parameter of the effective temperature $T_B \sim 1/m_B$ and $T^{**} \sim 1/m^{**}$ as,

$$\Omega_{T_{sc}} = \frac{1}{\lambda}(\Omega_{T_B} - \Omega_{T^{**}}), \quad (4)$$

where Grüneisen parameter is defined as $\Omega_T = -d(\log T)/d(\log V)$, and $\lambda = m^{**}/m_B$. If the main phenomena is due to the volume dependence of T_B , that is, the systems are mainly dependent on the Ω_{T_B} , T_{sc} and T_B will go to the same direction. In other word, T_{sc} will increase when the band mass m_B decreases. Basically it is the main argument that considering different strongly correlated electron system from heavy fermion systems to high T_{sc} oxides, T_{sc} scales the inverse of the specific heat coefficient γ ;^{23,24} basically SC can appear only below the Fermi temperature which is related to γ^{-1} . If the main phenomena is the volume dependence of T^{**} , which is observed in uranium heavy fermion compounds like UPt_3 , URu_2Si_2 and UBe_{13} , the Grüneisen parameter of the SC and normal phases have opposite sign.²⁵ The same trend is observed in URhGe.

Assuming the relation $A \sim (m^*)^2$, and that the upper critical field $H_{c2}(H)_{T \rightarrow 0}$ is governed by the orbital limit for this triplet superconductor, $H_{c2}(H)_{T \rightarrow 0}$ is given by the equation,

$$H_{c2}(H)_{T \rightarrow 0} \sim [m^*(H)T_{sc}^0(m_H^*)]^2, \quad (5)$$

one can estimate $T_{sc}^0(m_H^*)$ and $H_{c2}(H)$ for a given value of $A_c \sim (m_B)^2$. Figure 6 represents the predicted H dependence of $T_{sc}^0(m_H^*)$ and $H_{c2}(m_H^*)$ as a function of H for sample #1a, where $A_c = 1.1 \mu\Omega \text{ cm}/K^2$ is chosen, corresponding to the hypothesis of a field independent band mass m_B . Following our suggestions,²⁶ similar calculations were made,²⁷ however, no measurements were carried out for the field dependence of T^2 -law in the resistivity. As shown in the inset of Fig.5, the quadratic temperature dependence of the resistivity were observed at high fields.

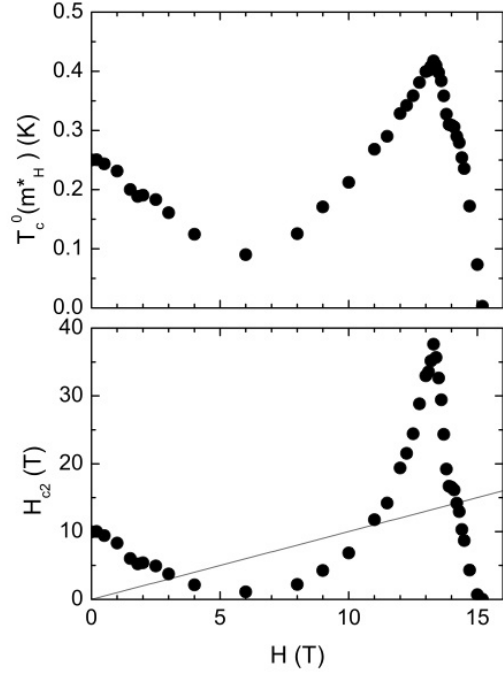


Fig. 6. (a) Calculated T_{sc} at zero field and (b) H_{c2} as a function of magnetic field. The solid line in panel (b) indicates the applied magnetic field. The superconductivity appears under the condition of $H_{c2} > H$.

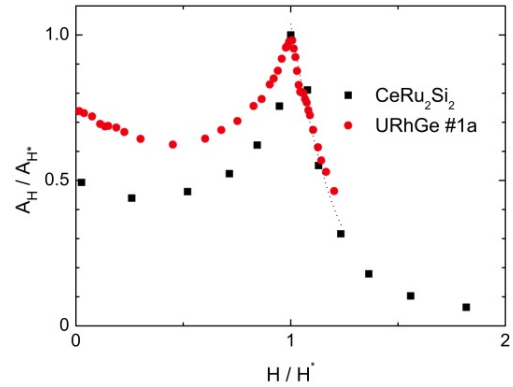


Fig. 7. (Color online) Relative field variation of A_H/A_H^* of URhGe (#1a) and $CeRu_2Si_2$ as a function of a normalized field H/H^* . The data of $CeRu_2Si_2$ is cited from Ref. 37.

Surprisingly, the predicted H_{c2} is in good agreement with the results of experiments, as shown in Fig. 6(b). T_{sc} at H_R is enhanced by a factor of 1.7, which is larger than the estimated value from the field variation of $\rho_0/\sqrt{A}$, as discussed above. Here we note that the $T_{sc}^0(m^*(H))$ strongly depends on the chosen value of A_c , namely m_B . When m_B increases, the evaluated $T_{sc}^0(m^*(H))$ increases as well.

URhGe is a good example where the RSC due to the

spin reorientation can be described by a field enhancement of the correlation, namely enhancement of m^{**} and invariance of m_B . The spin reorientation mechanism leads to escape from the rigidity of Ising spin dynamics. The fluctuation between c and b -axis component of the magnetization in the large field range may lead to a large field window of the mass enhancement, which is in agreement with the large field region of RSC. According to the neutron scattering experiments for $H \parallel b$, the sublattice magnetization for c -axis, M_c starts to decrease from 8 T and becomes zero at $H_R = 11.5$ T with increasing field.⁸ On the other hand, the sublattice magnetization for b -axis, M_b linearly increases from zero, and becomes $M_b = M_c$ at 10.5 T. Finally, M_b is fully polarized at $H_R = 11.5$ T. It means that the fluctuation between M_b and M_c starts to develop from 8 T. Simply thinking, when $M_b = M_c$ is realized, the magnetic fluctuation may become maximum, implying the large enhancement of the effective mass. This may correspond to a maximum value of A at a field, which is slightly lower than H_R defined as a peak of ρ_0 , as shown in Fig. 2. A fit of the resistivity ρ by a T^2 law lead to find another weak maxima of A for sample #1a and #1b. Its origin is left to the future study. It may be caused by the intrinsic effect due to a H crossover between collision and quantum criticality regime or the small misalignment inside the crystal.

On the other hand, for the other FM superconductor UGe₂, the field change of SC properties corresponds to a drastic switch in the description of the ferromagnetism: from perfectly polarized FM2 to imperfectly polarized FM1 according to the recent neutron scattering analysis.²⁸ For UGe₂, the Ising character is preserved at the switch from FM1 to FM2 at H_x , furthermore this switch is associated with a drop of m^* .^{29,30} The key phenomena for SC does not appear in the proximity to the ferromagnetic-paramagnetic (FM-PM) instability but in the instability at P_x , where the system may switch from FM2 to FM1. The pressure dependence of T_{sc} cannot be related to the pressure increase of γ term from FM2 to FM1, via an increase of m^{**} and application of the eq. (3). Obviously, the main phenomena is either a change in the Fermi surface topology as discussed in ref. 31 or another origin of pairing as proposed in the charge density wave scenario.^{32,33} At least in the frame of our model, T_B must change on both side of P_x . It is more complicated than the case of URhGe. The drastic change of Fermi surfaces in UGe₂ were reported between $P < P_x$ and $P > P_x$, but the experimental results between P_x and P_c are still unclear.^{34,35}

It is interesting to compare URhGe with CeRu₂Si₂, a heavy fermion compound highly studied for its metamagnetic transition at H_M where a sharp crossover occurs between a low field paramagnetic phase (PM) and a high field polarized paramagnetic (PPM) phase at $H_M = 7.7$ T. Figure 7 shows the relative field variation of A_H/A_{H^*} in reduced scale of H/H^* , where H^* corresponds to H_R and H_M for URhGe and CeRu₂Si₂, respectively. A perfect scaling occurs for $H/H^* > 1$, here both cases are governed by Ising ferromagnetic spin dy-

namics. Below $H/H^* < 1$, the systems are quite different. However, enhancement of $A(H^*)$ are rather similar, $A(H^*)/A(0) = 1.4$ and 2 for URhGe and CeRu₂Si₂, respectively.

Below H_M , microscopic phenomena are now well clarified in CeRu₂Si₂.³⁶ Antiferromagnetic (AF) correlation dominates below H_M and collapses just at H_M , where the FM fluctuation becomes soft in a narrow field window centered at H_M . As discussed in ref. 38, an interesting situation would occur, if CeRu₂Si₂ were SC at $H = 0$ with $H_{c2}^* > H_M$. Assuming the switch with the fluctuation from AF to FM, the singlet pairing may be replaced by the triplet pairing. Unfortunately, the Ising character of the AF spin dynamics presumably prevents the establishment of SC.

Thus the simplicity of URhGe is that the FM mechanism is preserved; furthermore as $T_{Curie} > T_{sc}$, the P and H dependence of a unique parameter m^{**} appears sufficient to describe the SC properties. Up to now for AF heavy fermion systems, only H reentrance of AF in the SC state of CeRhIn₅ has been reported;^{39,40} it corresponds to hierarchy between the bare parameters (T_N : Néel temperature, T_{sc} , H_c : critical magnetic field of the AF-PM boundary and H_{c2}): $T_{sc} > T_N$ and $H_c > H_{c2}(0)$; AF survives the normal phase up to H_c .

An interesting case will be that H_c is lower than H_{c2} , when $T_{sc} > T_N$. That may happen for CeCoIn₅ as no AF is detected above $H_{c2}(0)$, however, a new low temperature-high field superconducting phase is observed. In the framework of a magnetic scenario, one can imagine that the persistence of a SC gap inhibits the transition to PM phase which requires the collapse of the AF pseudogap; due to the interplay with SC, AF may be stucked to $H_{c2}(0)$. Up to now, the main trend is to neglect the possible magnetic origin, and to consider that the new phase of CeCoIn₅ is the evidence of the so-called FFLO state predicted four decades ago with a extra modulation of the order parameter along H .^{41–43} But still no definitive conclusion emerges from the experiments.⁴⁴

4. Conclusion

The reorientation of the moment from c to b -axis for $H \parallel b$ is characterized by an invariance of H_R on sample purity. While the RSC seems to strongly depend as its low field SC on the sample purity, indicating the unconventional nature for both RSC and low field SC. The T^2 Fermi liquid law of the resistivity is obeyed for all the field range, the amplitude of the A coefficient has an enhancement at H_R which is interpreted as an enhancement of the effective mass m^* . The enhancement of m^* appears to concern mainly the effective mass contribution m^{**} added by the magnetic correlation on the band mass m_B . The increase of m^{**} in the vicinity of H_R leads to a strong increase of the superconducting transition temperature T_{sc} and of the upper critical field $H_{c2} \sim (m^* T_{sc})^2$. Surprisingly, a crude model assuming McMillan-type formula for T_{sc} gives a good description of the experimental results. It is interesting to mention that the enhancement of the fluctuation is quite non symmetrical with respect to H_R . The feedback on SC is the

asymmetry of RSC boundary by reference to H_R . This property is clearly demonstrated in Fig. 7 by the comparison with CeRu_2Si_2 . The difference of re-entrant phenomena between in URhGe and in UGe_2 has been discussed. The particularity of UGe_2 is to involve SC pairing between quite different FM phases (fully polarized and partially polarized). The main phenomena appear to be the change in Fermi surface topology. At least for both cases, only FM is considered. For the re-entrant phenomena on appearance of a new low temperature and high field phase as observed in so-called Ce115 compounds, the antiferromagnetic fluctuations are dominant at $H = 0$. However, a field sweep will reveal the interplay between AF, PM, PPM and SC phase. CeRhIn_5 appears a simple case where the field re-entrance of AF disappears since the magnetic critical field H_c collapses rapidly under pressure. CeCoIn_5 is a more intriguing example, where AF may be stuck to $H_{c2}(0)$ over a rather large P window; as indicated an alternative explanation is the formation of a FFLO state.

Acknowledgements

We thank G. Knebel, J. P. Brison and F. Hardy for experimental supports and valuable discussion. A. M. has been supported by Research Fellowship of the Japan Society for the Promotion of Science for Young Scientists and EGIDE. This work was financially supported by French ANR projects ECCE and CORMAT.

- 1) W. A. Fertig, D. C. Johnston, E. DeLong, R. W. McCallum, M. B. Maple and B. T. Matthias: *Phys. Rev. Lett.* **38** (1977) 987.
- 2) D.E. Moncton, D.B. McWahn, P.H. Schmidt, G. Shirane, W. Thomlinson, M.B. Maple, H.B. MacKay, L.D. Woolf, Z. Fisk and D.C. Johnston, : *Phys. Rev. Lett.* **45** (1980) 2060.
- 3) S. S. Saxena, P. Agarwal, K. Ahilan, F. M. Grosche, R. K. W. Hasselwimmer, M. J. Steiner, E. Pugh, I. R. Walker, S. R. Julian, P. Monthoux, G. G. Lonzarich, A. Huxley, I. Sheikin, D. Braithwaite and J. Flouquet: *Nature* **406** (2000) 587.
- 4) D. Aoki, A. Huxley, E. Ressouche, D. Braithwaite, J. Flouquet, J.P. Brison, E. Lhotel and C. Paulsen: *Nature* **413** (2001) 613.
- 5) N. T. Huy, A. Gasparini, D. E. de Nijs, Y. Huang, J. C. P. Klaasse, T. Gortenmulder, A. de Visser, A. Hamann, T. Görlach and H. v. Löhneysen: *Phys. Rev. Lett.* **99** (2007) 067006.
- 6) E. Hassinger, D. Aoki, G. Knebel and J. Flouquet: *J. Phys. Soc. Jpn.* **77** (2008) 073703.
- 7) F. Hardy and A.D. Huxley: *Phys. Rev. Lett.* **94** (2005) 247006.
- 8) F. Lévy, I. Sheikin, B. Grenir and A. D. Huxley: *Science* **309** (2005) 1343.
- 9) F. Lévy, I. Sheikin and A. D. Huxley: *Nature Phys.* **3** (2007) 460.
- 10) V. Jaccarino and M. Peter: *Phys. Rev. Lett.* **9** (1962) 290.
- 11) H. W. Muel, C. Rossel, M. Decroux, Ø. Fischer, G. Remenyi and A. Briggs: *Phys. Rev. Lett.* **53** (1984) 497.
- 12) T. Konoike, S. Uji, T. Terashima, M. Nishimura, S. Yasuzuka, K. Enomoto, H. Fujiwara, B. Zhang and H. Kobayashi: *Phys. Rev. B* **70** (2004) 094514.
- 13) I. Sheikin, A. Huxley, D. Braithwaite, J. P. Brison, S. Watanabe, K. Miyake and J. Flouquet: *Phys. Rev. B* **64** (2001) 220503.
- 14) A. A. Abrikosov and L. P. Gor'kov: *Sov. Phys. JETP* **20** (1965) 7621.
- 15) D. Aoki, A. Huxley, F. Hardy, D. Braithwaite, E. Ressouche, J. Flouquet, J.P. Brison and C. Paulsen: *Acta Phys. Pol. B* **34** (2003) 503.
- 16) A. D. Huxley, S. J. C. Yates, F. Lévy and I. Sheikin: *J. Phys. Soc. Jpn.* **76** (2007) 051011.
- 17) F. Hardy, A. Huxley, J. Flouquet, B. Salce, G. Knebel, D. Braithwaite, D. Aoki, M. Uhlartz and C. Pfleiderer: *Physica B* **359-361** (2005) 1111.
- 18) F. Hardy, PhD thesis, Grenoble, (2004).
- 19) W. L. McMillan: *Phys. Rev.* **167** (1968) 331.
- 20) D. Fay and J. Appel: *Phys. Rev. B* **22** (1980) 3173.
- 21) T. R. Kirkpatrick, D. Belitz, Thomas Vojta and R. Narayanan: *Phys. Rev. Lett.* **87** (2001) 127003.
- 22) K. G. Sandeman, G. G. Lonzarich and A. J. Schofield: *Phys. Rev. Lett.* **90** (2003) 167005.
- 23) Y. J. Uemura, G. M. Luke, B. J. Sternlieb, J. H. Brewer, J. F. Carolan, W. N. Hardy, R. Kadono, J. R. Kempton, R. F. Kiefl, S. R. Kreitzman, P. Mulhern, T. M. Riseman, D. Li. Williams, B. X. Yang, S. Uchida, H. Takagi, J. Gopalakrishnan, A. W. Sleight, M. A. Subramanian, C. L. Chien, M. Z. Cieplak, G. Xiao, V. Y. Lee, B. W. Statt, C. E. Stronach, W. J. Kossler and X. H. Yu: *Phys. Rev. Lett.* **62** (1989) 2317.
- 24) T. Moriya and K. Ueda: *Rep. Prog. Phys.* **66** (2003) 1299.
- 25) J. Flouquet, J.P. Brison, K. Hasselbach, L. Taillefer, K. Behnia, D. Jaccard and A. de Visser: *Physica C* **185-189** (1991) 372.
- 26) J. Flouquet: private communications.
- 27) F. Lévy, PhD thesis, Grenoble, (2007).
- 28) N. Aso, G. Motoyama, Y. Uwatoko, S. Ban, S. Nakamura, T. Nishioka, Y. Homma, Y. Shiokawa, K. Hirota and N. K. Sato: *Phys. Rev. B* **73** (2006) 054512.
- 29) N. Tateiwa, T. C. Kobayashi, K. Hanazono, K. Amaya, Y. Haga, R. Settai and Y. Ōnuki: *J. Phys.: Condens. Matter*: **13** (2001) L17.
- 30) R. A. Fisher and N. D. Phillips: private communication.
- 31) T. Terashima, T. Matsumoto, C. Terakura, S. Uji, N. Kimura, M. Endo, T. Komatsubara and H. Aoki: *Phys. Rev. Lett.* **87** (2001) 166401.
- 32) S. Watanabe and K. Miyake, *J. Phys. Chem. Solids*: **63** (2002) 1465.
- 33) S. Watanabe and K. Miyake, *J. Phys. Soc. Jpn.* **71** (2002) 2489.
- 34) R. Settai, M. Nakashima, S. Araki, Y. Haga, T. C. Kobayashi, N. Tateiwa, H. Yamagami and Y. Ōnuki: *J. Phys.: Condens. Matter*: **14** (2002) L29.
- 35) T. Terashima, T. Matsumoto, C. Terakura, S. Uji, N. Kimura, M. Endo, T. Komatsubara, H. Aoki and K. Maezawa: *Phys. Rev. B* **65** (2001) 174501.
- 36) J. Flouquet, P. Haen, S. Raymond, D. Aoki and G. Knebel: *Physica B* **319** (2002) 251.
- 37) R. Boursier, A. Villaume, G. Lapertot, D. Aoki, G. Knebel and J. Flouquet: *Physica B* **403** (2008) 726.
- 38) J. Flouquet: *Prog. Low Temp. Phys. Vol. XV*, (2006) 139.
- 39) T. Park, F. Ronning, H. Q. Yuan, M. B. Salamon, R. Movshovich, J. L. Sarrao and J. D. Thompson: *Nature* **440** (2006) 65.
- 40) G. Knebel, D. Aoki, D. Braithwaite, B. Salce and J. Flouquet: *Phys. Rev. B* **74** (2006) 020501.
- 41) Y. Matsuda and H. Shimahara: *J. Phys. Soc. Jpn.* **76** (2007) 051005. and references there in.
- 42) P. Fulde and R. A. Ferrel: *Phys. Rev.* **135** (1964) A550.
- 43) A. I. Larkin and Yu. N. Ovchinnikov: *Zh. Eksp. Teor. Fiz.* **47** (1964) 1136. [*Sov. Phys. JETP* **20** (1965) 762.]
- 44) B.-L. Young, R. R. Urbano, N. J. Curro, J. D. Thompson, J. L. Sarrao, A. B. Vorontsov and M. J. Graf: *Phys. Rev. Lett.* **98** (2007) 036402.